

Information Sheet

COMPLETE TITLE OF THE PAPER:

Experimental Study for Swelling Potential of Water Swelling Material

SHORT TITLE WITHIN 60 CHARACTERS (If Applicable):

Swelling Potential of Water Swelling Material

CORRESPONDING AUTHOR:

Name: Shinya Inazumi
Affiliation: Graduate School of Engineering, Kyoto University
Fax no.: +81 75 383 3264
e-mail: inazumi@toshi.kuciv.kyoto-u.ac.jp

PRESENTING AUTHOR:

Name: Shinya Inazumi
e-mail: inazumi@toshi.kuciv.kyoto-u.ac.jp

Experimental Study for Swelling Potential of Water Swelling Material

S. Inazumi

Kyoto University, Kyoto, Japan (inazumi@toshi.kuciv.kyoto-u.ac.jp)

T. Wakatsuki

Nihon Chemical Paints Co., Ltd., Kanagawa, Japan (wakatsuki@ncpaint.co.jp)

M. Kobayashi

Nihon Chemical Paints Co., Ltd., Kanagawa, Japan (kobayashi@ncpaint.co.jp)

ABSTRACT Water-swelling material is a fluid sealant obtained by blending high absorbency polymer, a filler and a solvent by using a synthetic resin elastomer. In this research, we have studied the composition of water-swelling material, the extent of swelling and strength of the water swelling-material used as jointed water cut-off treatment material, by conducting various experiments. One of the examples of the results is that the adjustment of the degree of etherification of high absorbency polymer which is a component of the water-swelling material and the resin content of the synthetic elastomer contribute to the improvement of swelling and strength of the swelling material.

INTRODUCTION

Water-swelling material is a fluid sealant obtained by blending high absorbency polymer, a filler and a solvent by using a synthetic resin elastomer as the base material. In the field of civil engineering, water-swelling materials are widely used as water cut-off treatment material for increasing water cut-off properties at the joint section of steel sheet piles or steel pipe sheet piles (see Fig. 1) (Oki et al., 2003). Further, the water-swelling material coated or pasted to the joint section swells on contact with ground water, blocks the water passage gaps and allows water cut off at the joint section.

Recently, the “H-jointed steel pipe sheet piles with an H-H joint”, which is one of the newly developed methods for high water cut off, is being tried for application of water-swelling material for water cut-off treatment of the joints section. In a series of research projects, one can see a number of reports regarding the performance of water cut-off steel pipe sheet piles

making use of an H-H joint, using water-swelling material for adhesion (Inazumi et al., 2005; Inazumi & Kimura, 2009). For example in plain water or artificial sea water (3% saline), low hydraulic conductivity of the order of 1×10^{-8} cm/s has been clearly confirmed. Peeling off or the ability of water cut off of the water-swelling material at the field has been studied and good results have been reported in general.

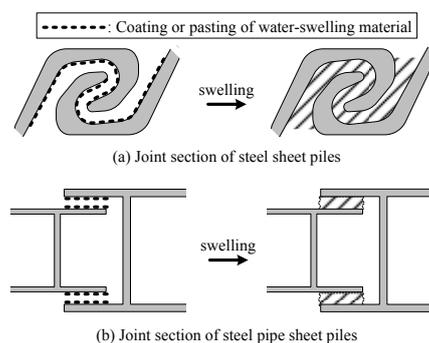


Fig. 1 Water cut-off treatment on joint section of steel sheet piles or steel pipe sheet using water-swelling materials

In this paper, we have carried out studies on the composition of water-swelling material and the strength of the swelling membrane, which is used for water cut-off treatment of the joint section of steel sheet piles or steel pipe sheet piles, by conducting various experiments for the purpose of improving the swelling ability and making it stronger.

HISTORICAL BACKGROUND

The water extracted from a dried film of water-swelling material fulfills the Food Sanitation Law Standards and is not harmful to the environment. At present, the composition of frequently used water-swelling materials (hereafter referred to as "current water-swelling material") is such that when it is soaked in plain water or sea water for 24 hours, it swells up to 15 - 30 times and 5 - 7 times, respectively, in terms of weight ratio. Thus, the current water-swelling material has extremely high swelling ability in plain water, nevertheless, the swelling percentage in sea water is 1/6 - 1/3 of that in plain water. Further, there is a tendency for the strength of the swelling material film (strength of water-swelling material after swelling) to be lower in plain water due to the effect of the water temperature. Because of this type of swelling and the strength properties of the swelling-type material, water-swelling material has, thus far, been used mainly as temporary water cut-off material. Here, the improvement in the swelling properties of the water-swelling material and the strength of the swelling material are not restricted only to increases in the water cut off at the joint section of the steel pipe sheet pile or steel sheet pile, but they may be contributing to several other applications of water-swelling material.

Representative examples of the application of water-swelling material includes vertical water cut off wall (barrier) built from steel sheets pile or steel pipe sheet pile in costal landfill sites. The vertical water cut-off property of steel sheets pile or steel pipe sheet piles is manifested by the swelling effect of water swelling material previously coated or pasted at the joints before setting up (*see* Fig. 1) (Oki et al., 2003). While

employing the water swelling material for water cut-off treatment of joints, it may be used in the form of a sheet pasted inside the joint (swelling-type sheet) or it may be used as a coated sealant. Depending upon the situation, it is possible to select the appropriate form of the material. Further, it is possible to prevent peeling off by synthesizing a swelling-type paint that adheres strongly to the steel. On the other hand, the water permeability factor of swelling-type material itself and that of the steel or paint are not different and both are of the order of 1×10^{-9} cm/s (Inazumi et al., 2005).

SWELLING PROPERTIES

Swelling Test

Here, the swelling properties of the water-swelling material were studied for various compositions, with water of different properties, different temperature and different pH, by designing individual tests.

The procedure for swelling tests was as follows:

- (i) A definite quantity of water-swelling material was dried, it was converted into a 2 mm thick sheet and a test piece sized 2 cm×2 cm was prepared.
- (ii) The initial weight of the test piece was measured and it was soaked in a water tank having various qualities of water at various temperatures.
- (iii) After soaking for 48 hours, it was taken out and the weight was measured.
- (iv) Swelling ratio (= weight after soaking / initial weight) was calculated.

The swelling ratio has been calculated by weight due to difficult in measuring volume of the water-swelling material after swelling. The swelling ratio by volume almost equaled 70% of it by weight, as a result of a preliminary test on swelling ratio of water-swelling material.

Composition and Swelling Ratio

Swelling mechanism of the water-swelling material depends mainly on the expansion of the high absorbency polymer (polymeric material designed to hold a large quantity of water). We

focused on the etherification (degree of substitution; DS value) of the polymer that is blended, and swelling experiments were conducted in the case of water-swelling material blended with polymers having different DS values. The DS value is an index showing the strength of bonds in the polymer structure. It is the molar quantity (number of mols) of sodium (Na) etherified (conversion into Na compound) corresponding to 1 unit (6 carbon atoms) of glucose (C₆H₁₂O₆) from the high absorbency polymer.

Figure 2 shows the swelling ratio of the water-swelling material soaked in plain water and artificial sea water (3% saline) and the DS value (of the high absorbency polymer). Moreover, the DS value of the high absorbency polymer used at present in water-swelling material is 0.6 M/c6. According to Fig. 2, when a polymer with a high DS value is used for blending, the swelling ratio in artificial sea water greatly increases. Especially by reforming the DS value of the high absorbency polymer to 0.9 M/c6, the swelling ratio increases 2 times of that of the current water-swelling material (High absorbency polymer DS value = 0.6 M/c6). This is because the insolubility of the high absorbency polymer is enhanced due to the large number of ions present in the artificial sea water. Nevertheless, the enhancement of insolubility is moderated by the use of high absorbency polymer with a high DS value, to a certain extent. On the other hand, in plain water (which does not enhance the insolubility of the water-swelling material) it is possible to maintain the swelling ratio of the same order (27 - 29 times) even if the DS value of high absorbency polymer is increased.

Figure 3 shows the relation between the addition ratio of the high absorbency polymer (having its DS value reformed to 0.9 M/c6 in water-swelling material) and its swelling ratio. From this it is understood that the increase in the addition ratio of high absorbency polymer contributes to the increase in swelling of water-swelling material in an environment comprising plain water and artificial sea water. Further, in general, the addition ratio of the high absorbency polymer

currently used for blending with water-swelling material (high absorbency polymer with a DS value = 0.6 M/c6) is 32.5% by weight.

Thus, for further improvement of the swelling ratio of the water-swelling material, it is proposed to ensure blending of high absorbency polymer having a DS value in excess of DS = 0.6 M/c6 and with more than 32.5% by weight.

Salinity of Soaking Water, Its Temperature, pH and the Swelling Ratio

The properties of the soaked water (salinity, plain water or sea water), water temperature and pH are supposed to greatly influence the swelling property of the water-swelling material. For this, swelling experiments were carried out by varying the conditions like the quality of soaked water, its temperature and pH.

Depending upon whether the soaking water is

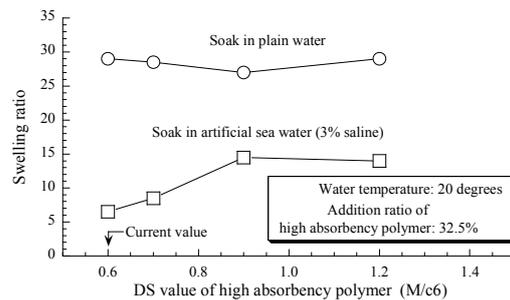


Fig. 2 Relationship between swelling ratio and DS value of high absorbency polymer for water-swelling material

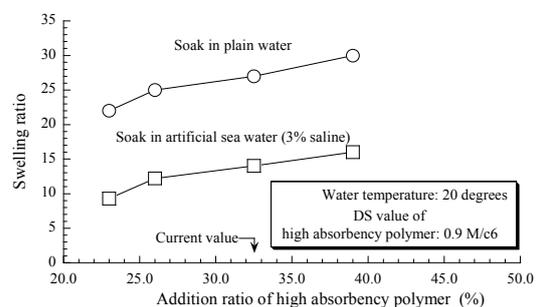


Fig. 3 Relationship between swelling ratio and addition ratio of high absorbency polymer for water-swelling material

plain water or artificial sea water (3% saline) there is a large difference in the swelling ratio of the water-swelling material. On the other hand, in the case of a high absorbency polymer with a reformed DS value of around 0.9M/c6, the swelling ratio increases a lot, especially in the case of artificial sea water (3% saline) as stated in above, and it is possible to get a swelling ratio twice that of the value found in a case utilizing the currently used high absorbency polymer with a DS value = 0.6 M/c6. As a result, the difference between the swelling ratio in an environment of plain water and artificial sea water declines (see Fig. 2).

As shown in Fig. 4, the temperature of the soaking water influences the swelling ratio of the water-swelling material and, especially in the case of the plain water environment, the swelling ratio shows a tendency to increase as the water temperature increases. On the other hand, increasing the temperature of artificial sea water

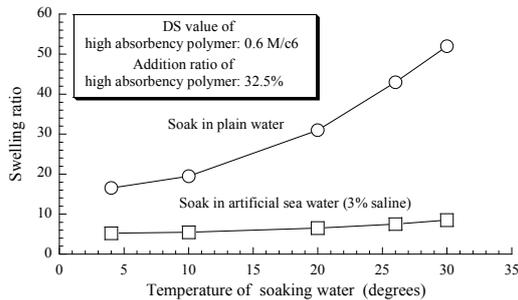


Fig. 4 Relationship between swelling ratio and temperature of soaking water for water-swelling material

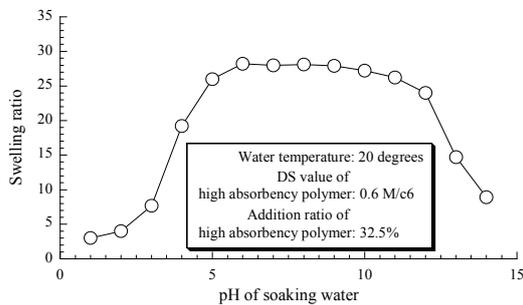


Fig. 5 Relationship between swelling ratio and pH of soaking water for water-swelling material

does not improve the swelling ratio of the water-swelling material. The high absorbency polymer blended with water-swelling material is a high polymer electrolyte and, when it is soaked in an aqueous environment, water gets absorbed in the mesh of the high absorbency polymer and it is gelatinized (swollen condition). Further, the gelatinized high absorbency polymer dissolves in water, giving rise to a uniform polymer solution. However, the high absorbency polymer has the property of bonding with polyvalent metal ions and if polyvalent metal ions exist in the water, it forms insoluble metal salts. The formation of insoluble metal salts restricts the free movement of the molecules, and as a result, only gel formation (swelling) unidirectional water absorption into the high absorbency polymer occurs. Moreover, increasing the water temperature enhances the quantity of water absorbed into the high absorbency polymer (swelling is enhanced) more. On the other hand, in an artificial sea water environment, as the ionic concentration is high, the water content that the high absorbency polymer can absorb may reduce (insolubility is enhanced and swelling becomes less). Thus, the insolubility of high absorbency polymer is enhanced and, when the swelling ratio of the water-swelling material itself is small (under the artificial sea water environment), the increase in the swelling ratio may also be prevented as the temperature goes up.

Figure 5 shows the relation between pH of the soaking water and of the swelling ratio of the water-swelling material. From this, it is understood that the water-swelling material has a tendency to have a lower swelling ratio in a strongly acidic or strongly alkaline area. However, if the pH is in the area of 4 - 12, the influence of pH on the swelling ratio is less and thus in the actual use of water-swelling material, pH of soaked water does not have a great influence.

STRENGTH CHARACTERISTICS

Water-swelling Material Strength Test

Water-swelling material strength means the strength of the material when the water swelling-material is in a swollen condition.

Swelling material strength of the water-swelling material greatly influences the resistance to water (hydraulic) pressure and long-term endurance. Thus, a study was conducted from various viewpoints for improving the strength of swelling material, and it was concluded that the composition of water-swelling material is the factor behind this. Here, the swelling strength of the water-swelling material was measured by using a small desk testing machine (EZTEST-500N, SHIMADZU Corporation) and penetrating elastic tool (diameter 3 mm) (see Fig. 6) and, the relation of the composition of the water-swelling material with the swelling strength was studied. The swelling material strength was defined as the strength required (by the penetration elastic tool with a 3 mm diameter), for penetration and breaking of the water-swelling material.

The procedure for the swelling film strength test was as follows:

- (i) A definite quantity by weight of water-swelling material was dried, it was converted into a 2 mm thick sheet and a test piece sized 2 cm×2 cm was prepared.
- (ii) The test piece was submerged in a water tank filled with plain water and artificial sea water at a set temperature.
- (iii) After submerging for 48 hours, the penetration tool (3 mm diameter) was slowly allowed to penetrate into the water-swelling material as shown in Fig. 6 and the swelling material strength (penetration elasticity value) was measured.

Composition and Swelling Material Strength

Synthetic resin elastomer, which is the base

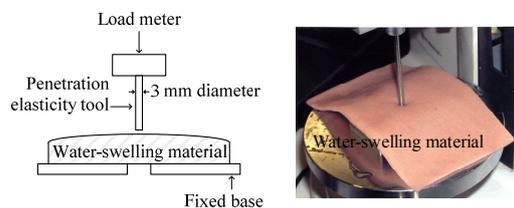



Fig. 6 Simple overview of water-swelling material strength test

material for the water-swelling material, is one of the materials that influences the swelling film strength. Here, attention was paid to the resin content (vinyl acetate) of the synthetic resin elastomer, and swelling material strength tests were carried out in the case of water-swelling material blended with elastomer B and elastomer C (having a resin content 1.3 times and 1.5 times that in the synthetic resin elastomer A, which is used for blending with the current water-swelling material).


Table 1 shows the swelling ratio and the swelling material strength of the water-swelling material soaked in plain water and artificial sea water at 20°C water temperature. Further, Fig. 7 shows swelling material strength with the variation of the temperature of the soaking plain water or artificial sea water. Table 1 shows that the swelling ratio of the water-swelling material decreases according to the synthetic resin elastomer content blended with it. However, when blended with elastomers B or C, which have a higher resin content, the swelling material strength increases in plain water and artificial sea water. Especially water-swelling material blended with a higher quantity of synthetic resin elastomer B can increase the swelling film strength to about 2 times and 1.5 times that of the currently used water-swelling material in plain water and artificial sea water, respectively. The increase in the swelling material strength by blending with elastomer B and C is manifested in the case of both a plain water and artificial sea water environment under a water temperature of 5 - 30°C (see Fig. 7). On the other hand, the swelling material strength blending with each elastomer shows the tendency to decrease with the increase of water temperature in the case of both a plain water and artificial sea water. Furthermore, the decrease in the strength under the artificial sea water environment may be confirmed to be larger than that under the plain water environment. However, it is thought that the strength decreasing rate of the sea water environment and that under the plain water environment are the almost the same levels. Also, no much difference in the decreasing tendency in both swelling ratio and

Table 1 Swelling ratio and the swelling material strength of water-swelling material soaked in plain water and artificial sea water at 20 °C water temperature

Elastomer	Swelling ratio		Strength (N)	
	Plain water	Artificial sea water	Plain water	Artificial sea water
Elastomer A	31	15	0.3	1.0
Elastomer B	28	14	0.6	1.3
Elastomer C	24	11	1.0	1.8

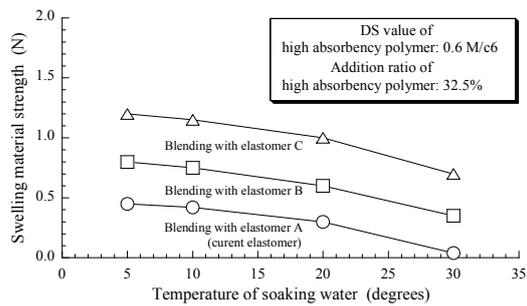

(a) Soaking in plain water

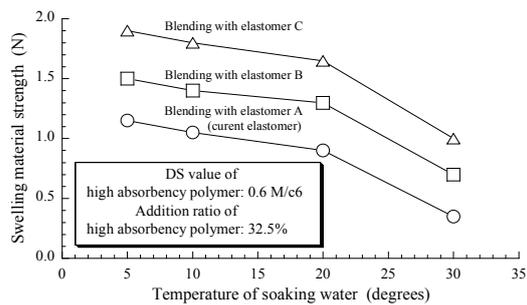

(b) Soaking in artificial sea water

Fig. 7 Relationship between swelling material strength and temperature of soaking water for water-swelling material

swelling material strength was seen between two cases of plain and artificial sea water (*see* Figs. 4 and 7).

CONCLUSIONS

- (1) In case of water-swelling material blended with high absorbency polymer with higher etherification value (DS value), the swelling ratio is very high in artificial sea water. Especially, by reforming the DS value of the high absorbency polymer to 0.9 M/c6,

swelling ratio that is 2 times the value of that of the currently used water-swelling material (with a DS value of the high absorbency polymer = 0.6 M/c6) can be obtained in an artificial sea water environment.

- (2) An increase in the water temperature of plain water influences the increase in the swelling ratio of the water-swelling material. On the other hand, the temperature of sea water does not influence the swelling ratio of the water-swelling material. Further, water-swelling material shows a tendency of lowering the swelling ratio in strongly acidic or strongly alkaline areas, but the influence of pH on the swelling ratio of the water-swelling material is less in the area of pH 4 - 12.
- (3) The quantity of synthetic resin elastomer, which is a component of the water-swelling material, contributes to the improvement of the swelling film strength of the water-swelling material. Especially water-swelling material blended with a higher quantity of synthetic resin elastomer B can increase the swelling film strength to about 2 times and 1.5 times that of the currently used water-swelling material in plain water and artificial sea water, respectively.

REFERENCES

- Oki, T. et al. (2003): Evaluation of impermeability performance of the vertical impermeable walls by using steel sheet piles and steel pipe sheet piles (in Japanese), Proc. of the 5th Japan National Symposium on Environmental Geotechnology, pp.53-58.
- Inazumi, S. et al. (2005): Performance of H-jointed steel pipe sheet piles with H-H joint in vertical hydraulic cutoff walls, Proc. of the 16th Int. Conf. on Soil Mechanics and Geotechnical Engineering, Vol.4, pp.2269-2272.
- Inazumi, S. and Kimura, M. (2009): On-site verification for installation and permeability of H-jointed SPSPs with H-H joints, Proc. of the 17th Int. Conf. on Soil Mechanics and Geotechnical Engineering, Vol.3, pp.2540-2543.